

THE "A" Coatings in Manufacturing Engineering

11th Conference PROCEEDINGS



EDITORS:
K.-D. Bouzakis
K. Bobzin
B. Denkena
M. Merklein

1-3 October 2014
Thessaloniki, Greece

THE "A" Coatings
11th International Conference
in Manufacturing Engineering

PROCEEDINGS

ISBN 978-960-98780-8-1

Thessaloniki - Greece

Printed by



18th klm Thessaloniki - Perea
P.O. Box 4171 – 570 19 Perea -Thessaloniki
Tel.: +30 2392 072.222 – Fax: +30 2392 072.229
e-mail: info@ziti.gr

www.ziti.gr

Contents

Plenary

<i>Innovative test methods of PVD and DC coated cutting tools to explain their performance at dynamic loads and elevated temperatures</i> K.-D. Bouzakis	3
<i>Interdependencies of residual coating stresses and process parameters with respect to tool life in turning of AISI 1045</i> B. Breidenstein, B. Bergmann, B. Denkena, R. M'Saoubi, J. Andersson	5
<i>Tribology in sheet-bulk metal forming processes- Interaction of Tailored Surfaces Coatings and Material Flow</i> M. Merklein, M. Löffler, U. Vierzigmann	7
<i>Application oriented design of PVD-Coatings for tools and components</i> K. Bobzin, N. Bagcivan, M. Ewering, T. Brögelmann	9

Coatings in Manufacturing

<i>Brittleness and fatigue effect of mono- and multi-layer PVD films on the cutting performance of coated cemented carbide inserts</i> G. Skordaris, K.-D. Bouzakis, P. Charalampous, E. Bouzakis, R. Paraskevopoulou, O. Lemmer, S. Bolz	13
<i>On the tribological influence of coatings in cold forging</i> K. Andreas, M. Merklein	23
<i>Effect of cutting edge preparation of coated tools on their performance in milling various materials</i> K.D. Bouzakis et al	33
<i>A new generation of PVD coatings for high-performance gear hobbing</i> A. Lümke, M. Beutner, M. Morstein, M. Köchig, M. Wengler, T. Cselle, B. Karpuschewski	53
<i>Effect of silicon content on PVD film mechanical properties and cutting performance of coated cemented carbide inserts</i> K.-D. Bouzakis, E. Bouzakis, S. Kombogiannis, R. Paraskevopoulou, G. Skordaris, S. Makrimalakis, G. Katirtzoglou, M. Pappa, S. Gerardis, R. M'Saoubi, J.M. Andersson	65
<i>Nitride and oxy nitride PVD coatings for application in plastics processing</i> N. Bagcivan, K. Bobzin, R. H. Brugnara	79

<i>Innovative tribological systems in sheet metal forming – Revolution in the press shop?,</i> K. Andreas, J. Steiner, U. Vierzigmann, M. Merklein, S. Tremmel, R. Zhao	87
<i>Coated tools' performance in up and down milling stainless steel, explained by film mechanical and fatigue properties</i> K.-D. Bouzakis, S. Makrimalakis, G. Skordaris, E. Bouzakis, S. Kombogiannis, G. Katirtzoglou, G. Maliaris	97
<i>HPPMS Alumina coatings deposited at various bias</i> K. Bobzin, N. Bagcivan, R.H. Brugnara, S. Basturk	117
<i>Wear estimation of coated tools in milling high resistance hardened steels based on entry impact duration</i> K.-D. Bouzakis, R. Paraskevopoulou, P. Charalampous, T. Kotsanis, G. Katirtzoglou, S. Makrimalakis	127
<i>Research the wear resistance of multilayer coating Ti/TiN/TiCN-ml on 1.2343 steel</i> G. Mishev, V. Rupetsov, S. Dishliev, C. Pashinski	139
<i>Interdependencies of residual coating stresses and process parameters with respect to tool life in turning of AISI 1045</i> B. Breidenstein, B. Bergmann, B. Denkena, R. M'Saoubi, J. Andersson	149

Properties of Further Coatings and Applications

<i>Development of coated milling cutters based on the chip formation mechanisms and coating and substrate properties investigated by innovative methods</i> K.-D. Bouzakis, M. Batsiolas, E. Bouzakis, G. Giannopoulos, S. Kombogiannis, S. Makrimalakis, N. Michailidis, G. Skordaris, A. Tsouknidas, F. Klocke, T. Berg, M. Busch, M. Ottersbach	161
<i>Feasibility study of friction stir processing on thick aluminum cold sprayed coating</i> D.I. Pantelis, P.N. Karakizis, N.M. Daniolos, S.A. Alexandratos, I.G. Papantoniou	169
<i>Adhesion characterization of dlc coatings On steel specimens by inclined impact tests</i> K.-D. Bouzakis, P. Charalampous, G. Skordaris ¹ , F. Dimofte, N.M. Ene, R. Ehinger, S.Gardner, B.S. Modrzejewski, and J.R. Fetty	178a
<i>Combined application of nickel-based filling-metal with hot-gas corrosion protective coatings using thermal spraying and subsequent heat-treating for near-net shape repairs of turbine blades</i> M. Nicolaus, K. Möhwald, H. J. Maier	179
<i>Mechanical and wear behavior of Titania Plasma sprayed coatings</i> A. Koutsomichalis, N.M. Vaxevanidis, A. Venci, P. Psyllaki	185
<i>Investigation of corrosion fatigue durability for a 7075 aluminum alloy subjected to blasting and anodizing</i> N. Michailidis, F. Stergioudi, A. Ragousis, G Maliaris	193

<i>Study on wear resistance of TiO₂ sprayed coatings. Correlation between deposition parameters and wear properties</i>	
M. Kandeва, V. Blaskov, I. Stambolova, N.G. Kostova, A. Eliyas, K. Balashev, S. Vassilev	203
<i>A dynamic FEM simulation of the nano-impact test on on mono- or multi-layered PVD films with various structures considering their graded strength properties determined by experimental-analytical procedures</i>	
G. Skordaris, K.-D. Bouzakis, P. Charalampous	211
<i>Fatigue strength of diamond coatings' interface assessed by inclined impact test</i>	
K.-D. Bouzakis, G. Skordaris, E. Bouzakis, S. Makrimalakis, S. Kombogiannis, O. Lemmer	227
<i>Fatigue strength of diamond coatings' interface assessed by inclined impact test at elevated temperatures</i>	
E. Bouzakis, K.-D. Bouzakis, G. Skordaris, P. Charalampous, S. Kombogiannis, O. Lemmer	239
<i>High wear and fracture resistant carbon based coatings</i>	
M. Kot, Ł. Major, J. Lackner, W. Rakowski	255
<i>Strain rate effect on the fatigue failure of thin PVD coatings: An investigation by a novel impact tester with adjustable repetitive force</i>	
K.-D. Bouzakis, G. Maliaris, S. Makrimalakis	265
<i>Quantification of PVD film adhesion with critical shear stress by using dynamic simulation of the inclined impact test</i>	
G. Skordaris	281
<i>Influence of surface treatment on corrosion behavior of open-cell aluminum foams</i>	
C.A. Vogiatzis, F. Stergioudi, K. Gkrekos, N. Michailidis, S. Skolianos	291
<i>Evaluation of the carburization of high temperature alloys</i>	
G.F. Samaras, G.N. Haidemenopoulos	301
<i>Study of Al₂O₃- Aluminum matrix composites fabrication using friction stir processing technique</i>	
D.I. Pantelis, P.N. Karakizis, N.M. Daniolos, S.A. Alexandratos, I.G. Papantoniou	309
<i>Abrasive wear of chemical Nickel coatings with boron nitride nano-particles</i>	
M. Kandeва, A. Vencl, E. Assenova, D. Karastoyanov, T. Grozdanova	319
<i>Production of carburized aluminum foams and evaluation of their mechanical responses</i>	
F. Stergioudi, N. Michailidis, A. Tsouknidas	327
<i>Coatings' properties assessment via nanoindentations, perpendicular and inclined impact test at ambient and elevated temperatures</i>	
K.-D. Bouzakis, E. Bouzakis, G. Skordaris, S. Makrimalakis, T. Kotsianis	337
<i>Tribological behavior of solid lubricants-polyester composites coatings</i>	
O. Dodun, L.Slătineanu, M. Coteață, G. Nagiț	351

INDustrial presentations

<i>Diamond coatings for the machining of composite materials used in aerospace industry</i> <i>W. Kölker, O. Lemmer, B. Mesic, C. Schiffers, M. Frank, M. Wodal</i>	363
<i>Wear and friction understanding of coated cutting tools - an industrial approach</i> <i>M. Fallqvist, J. Andersson, R. M'Saoubi</i>	365
<i>Erosion Protection in Modern Jet Engine Compressors by means of PVD-Multi Layer Coatings</i> <i>P. Jaschinski, T. Takahashi, R. Cremer</i>	367
<i>Correlation of microstructure and thermal conductivity in high AL-containing Ti-AL-N coatings</i> <i>R. Rachbauer, D. Kurapov, M. Arndt, M. Bartosik, P.H. Mayrhofer</i>	369

ABRASIVE WEAR OF CHEMICAL NICKEL COATINGS WITH BORON NITRIDE NANO-PARTICLES

M. Kandeва¹, A. Venci², E. Assenova³, D. Karastoyanov⁴, T. Grozdanova⁵

1. Technical University - Sofia, Faculty of Industrial Engineering, Tribology Center, Sofia, Bulgaria
2. University of Belgrade, Faculty of Mechanical Engineering, Tribology Laboratory, Belgrade, Serbia
3. Society of Bulgarian Tribologists, Sofia, Bulgaria, emiass@abv.bg
4. Institute for Information and Communication Technologies, Bulgarian Academy of Sciences, Sofia, Bulgaria
5. Space Research and Nanomaterials Institute – Bulgarian Academy of Sciences, Sofia, Bulgaria

ABSTRACT

Using the disk-abrasive roller test rig, wear behaviour of chemical Ni coatings containing boron nitride nanoparticles has been studied. The coatings were deposited by means of EFTOM-Ni technology method patented at the Technical University - Sofia. Comparative study has been done of wear resistance of the heat treated (heating during 6 h at 300°C) and as deposited (no additional heat treatment) coatings, correspondingly with contents of particles of 10 µm averaged size and without nanoparticles addition.

KEYWORDS: Electroless deposition, Nickel coatings, BN nanoparticles, Abrasive wear

1. INTRODUCTION

The study deals with improvement of the wear resistance of working shafts (calenders) involved in the production of sheet-formed and foliate materials – paper, cardboard, leather, etc. Calender shafts work in dynamic conditions, i.e. in various temperature and contact interaction regimes, and are subjected to severe wear [1,2]. Usually, their resource is improved through wear resistant thin and hard Cr coatings. A team of researchers from the Institute for Information and Communication Technologies at the Bulgarian Academy of Sciences and the Mechanical Engineering Faculties in TU-Sofia and Belgrade develop a Project aiming replacement of the ecology non-friendly industrial Cr by Ni chemical coatings. High wear resistance is achieved through imbedding of various nano- and micro-size particles (SiC, diamond, BN, etc.) in the coating [3-5].

The Ni chemical coatings are obtained by the method of chemical electroless (no external source of electric current) deposition, also known as the “Electroless nickel plating”. This method is a reduction process between the positive metal ions M^{z+} and negative electrons e^- :



where z is the valence of the metal ion.

The necessary electrons are obtained as result of chemical reaction between the solution containing the salt of the considered metal and the surface of the sample to be coated. In this reaction the Ni ions of the solution, according to their valence, accept a certain number of electrons and the metal ions transform in neutral atoms (Me), which build gradually the crystal lattice of the coating [6,7].

The paper considers a comparative study of the wear properties of Ni chemical coatings containing boron nitride (BN) nanoparticles concerning both heat treated and non heat treated coatings.

2. COATINGS DEPOSITION AND EXPERIMENTAL DETAILS

Four type of chemical Ni coatings have been studied under equal conditions of dry sliding abrasion: 1) Ni coating without nanoparticles in as deposited conditions; 2) Ni coating without nanoparticles and with additional heat treatment (heated at 300 °C during 6 hours); 3) Ni coating containing BN nanoparticles of average size 10 nm in as deposited conditions; 4) Ni coating containing BN nanoparticles of average size 10 nm and with additional heat treatment (heated at 300 °C during 6 hours). Designation of tested coatings and their microhardness are shown in Table 1 gives the description of the samples.

Table 1. Designation and microhardness of tested coatings

Sample	Coating	Designation	Microhardness HK 0.02
1	Ni non-heated	Ni	790
2	Ni heated at 300 °C for 6 h	Ni ^{HT}	860
3	Ni with BN nanoparticles non-heated	Ni-BN	456
4	Ni with BN nanoparticles heated at 300 °C for 6 h	Ni-BN ^{HT}	1050

HT – heat treated

The coatings are obtained under equal conditions: composition, concentration and temperature of the chemical solution, time of coating deposition, and nanoparticle concentration of 5 vol. %. The coatings are deposited on steel specimens with composition given in Table 2.

Table 2. Chemical composition (wt. %) of the coated material (substrate)

Element	C	S	Mn	P	Si	Cr	Ni	Fe
Percentage	0.4	0.045	0.55	0.45	0.20	0.30	0.30	Balance

The specimens are round disks with 100 mm diameter and 3 mm thickness, with equal roughness of $R_a = 0.453 \mu\text{m}$ measured by profilometer TESA Rugosurf 10G (Figure 1).

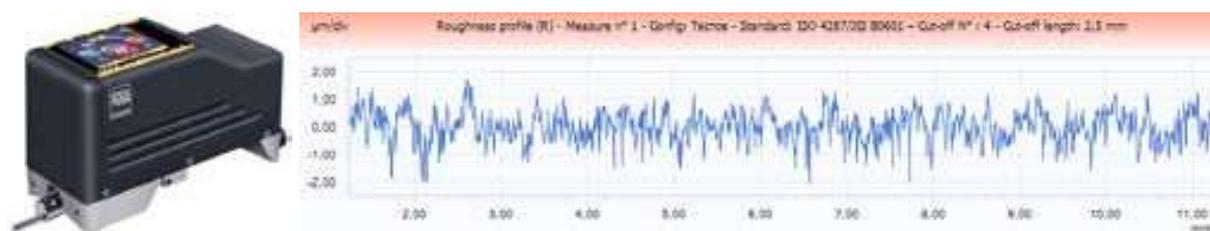


Figure 1: TESA Rugosurf 10G and sample roughness profile.

The microhardness is determined using Knoop method with 0.2 N load (Table 1). Coatings with thickness of 12.5 μm are created. The thickness is obtained as average value of 10 measurements by the device Pocket-LEPTOSKOP 2021 Fe (Figure 2) on both sides of the disk.

The abrasive wear tests are done using the disc-abrasive roller rig (Figure 3). A disc specimen (1) with coating (2) is fixed on the horizontal base disk (3) driven with constant rotational speed of 60 rpm by electric motor (4). Abrasive roller (5), Taber abrading wheel Calibrase[®] CS-10, is mounted on horizontal axis (6) and provides through weights (8) the necessary normal load (P)

in the contact zone (K). Abrasive roller with thickness of 13 mm is driven with constant rotational speed. Wear is determined as the difference between the initial specimen mass and its mass after given number N of cycles counted by the counter (7). The mass is measured by the electronic balance WPS 180/C/2 with 0.1 accuracy.



Figure 2: Pocket-LEPTOSKOP 2021 Fe

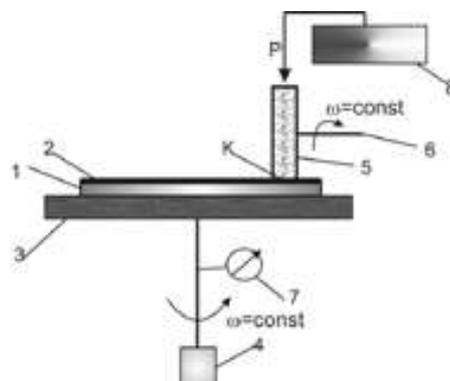


Figure 3: Principle scheme of the disk-abrasive roller tribometer

All coatings are studied at equal load of 2.5 N. The average sliding speed was app. 0.232 m/s. The sliding distance (s) is calculated by the Equation (2):

$$s = 2r \cdot \pi \cdot N \quad (2)$$

where $r = 37$ mm is the distance between the rotational axis of disc specimen (1) and the mass centre of the contact area (K), see [Figure 3](#), and N is the number of rotating cycles.

Wear of the coatings are determined at various number of cycles, i.e. at $N = 200, 400, 600$ and 800 , and corresponding wear curves are constructed. Mass wear rate (W_m) in mg/m is calculated by fitting the wear curves (it is the slope of wear curve), assuming that the steady-state wear was from the beginning of the tests (which is common thing for the abrasion wear). Linear wear rate is more convenient for engineering practice than mass wear rate. Linear wear rate (W_h) in mm/m, i.e. the intensity of the coating thickness loss (h) is calculated by the Equation (3):

$$W_h = \frac{h}{s} = \frac{m}{s \cdot \rho \cdot A_n} = \frac{W_m}{\rho \cdot A_n} \quad (3)$$

where m is the mass loss in mg, $\rho = 7.8$ mg/mm³ is the coating density, and $A_n = 3.02 \times 10^3$ mm² is the coated disc specimen wear area (ring with outer radius of 43.5 mm and inner radius of 30.5 mm).

Influence of heat treatment and addition of BN nanoparticles on the reduction of wear rate are analysed by comparing the wear rates of testing coatings. These influences are expressed in percentage through the reduction index (Equation 4), which is the ratio of the difference of both specimen wear rate and the wear rate of the reference specimen.

$$R_{i,j} = \frac{W_{hi} - W_{hj}}{W_{hi}} \times 100, \% \quad (4)$$

3. RESULTS AND DISCUSSION

Experimental results for mass wear at various cycle numbers are given in Table 3.

Table 3. Abrasive wear of tested coatings

Test parameter			Coating designation			
Number of cycles	Sliding distance, m	Time, min	Ni	Ni ^{HT}	Ni-BN	Ni-BN ^{HT}
			Mass loss, mg			
200	46.5	3.33	2.5	1.5	1.5	0.5
400	93.0	6.66	4.4	2.0	2.0	1.4
600	139.5	10	6.2	2.5	3.8	1.7
800	186.0	13.33	6.6	3.3	4.4	1.8

Using the results from Table 3, wear curves are constructed, correspondingly in [Figure 4](#) for coatings without nanoparticles and in [Figure 5](#) for coatings with BN nanoparticles.

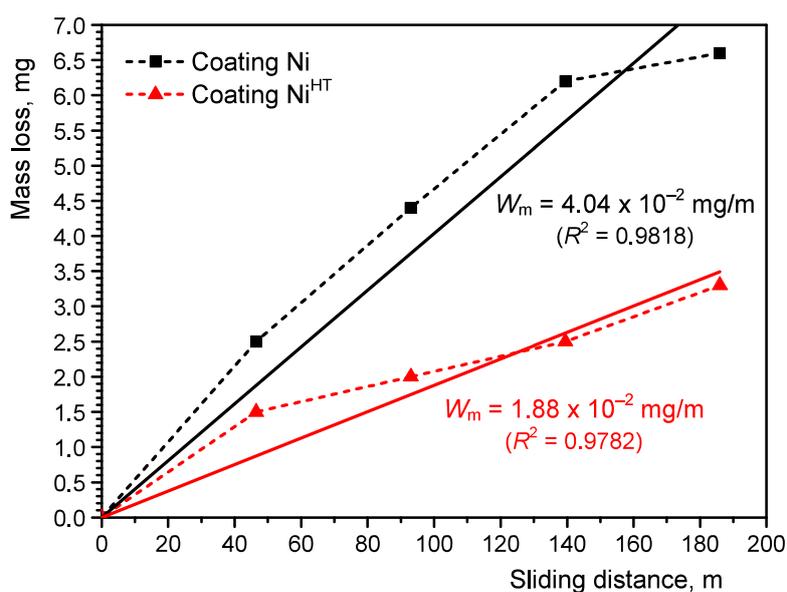


Figure 4: Mass loss vs. sliding distance for Ni coatings without nanoparticles (with and without additional heat treatment)

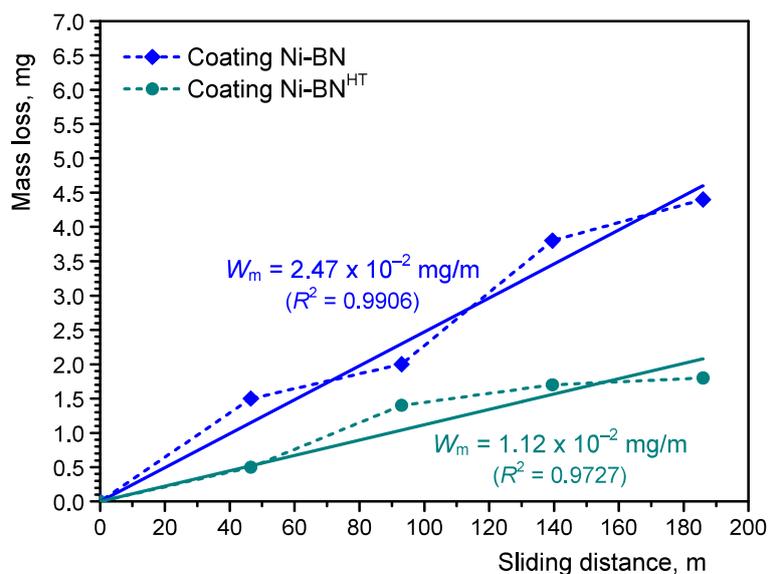


Figure 5: Mass loss vs. sliding distance for Ni coatings with BN nanoparticles (with and without additional heat treatment)

The heat treatment leads to reduction of wear for both version of Ni coating (with and without BN nanoparticles). The highest mass wear rate (W_m) of 4.04×10^{-2} mg/m is observed for as deposited Ni coating without BN particles, and the lowest mass wear rate of 1.12×10^{-2} mg/m for heat treated Ni coating with BN particles. The wear process is more stable for as deposited coatings, which can be seen from the R^2 (R-squared) value. Influence of imbedded BN nanoparticles on wear process stability can be neglected. Generally all R-squared shows acceptable goodness of fit ($R^2 = 1$ is a perfect fit).

Linear wear rate, i.e. the intensity of the coating thickness loss is calculated from mass wear rate by the Equation (3), and the results are shown in Table 4. In order of easier comparison of different coatings, a value of relative wear rate is also introduced (relative to the sample 1, i.e. coating Ni).

Table 4. Linear wear rate and the influence of heat treatment and addition of BN nanoparticles on the reduction of wear rate

Sample	Coating	Wear rate, $\mu\text{m/m}$	Relative wear rate	Influence of heat treatment, %		Influence of BN nanoparticles, %	
				without particles	with particles	as deposited	heat treated
1	Ni	1.71×10^{-3}	1				
2	Ni ^{HT}	7.97×10^{-4}	0.47				
3	Ni-BN	1.05×10^{-3}	0.61	$R_{1,2} = 53.5$	$R_{3,4} = 54.8$	$R_{1,3} = 38.7$	$R_{2,4} = 40.5$
4	Ni-BN ^{HT}	4.74×10^{-4}	0.28	Average: R = 54 %		Average: R = 40 %	

Comparative quantitative assessment of the wear rate reduction is done through the reduction index (R), Table 4. Heat treatment shows higher influence on wear reduction than imbedding of BN nanoparticles. With heat treatment an average reduction of wear was 54 %, and with imbedding of BN nanoparticles wear reduction of about 40 % is obtained. Nevertheless, both influences on wear reduction are significant. Obviously the highest wear reduction of 72 % was noticed for heat treated Ni coating with imbedded BN nanoparticles.

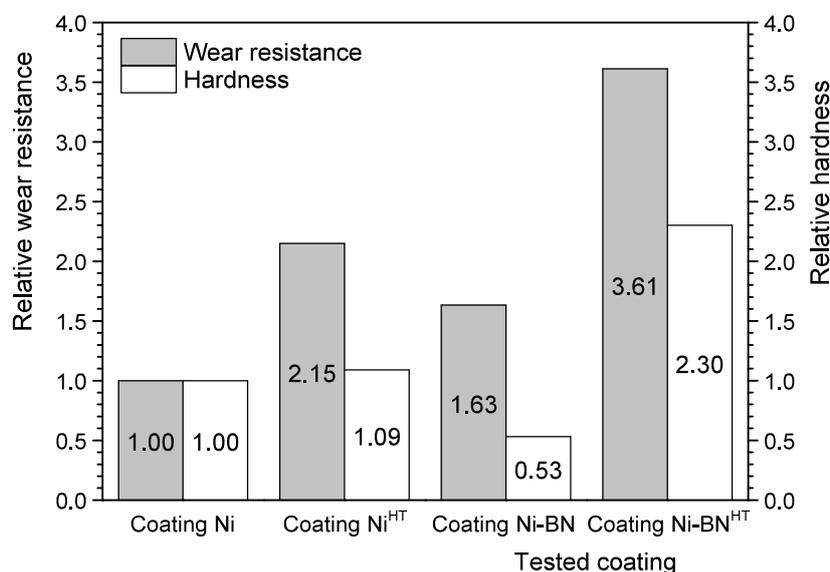


Figure 6: Comparative values of relative wear resistance and relative hardness of tested coatings

In addition to the wear data, the hardness of each of tested materials was determined (Table 1), as an ancillary mechanical property, to make appropriate correlations. It is well known that hardness of commercially pure metals influences its abrasive wear resistance and that higher hardness implies a higher wear resistance. Khrushov [8] finds out that increase of the wear resistance depends on the way in which the metal is being hardened (alloying, heat treatment or

work-hardening) and that in some cases wear resistance decreases with increase of hardness. The results of other researchers also show that abrasion wear resistance of quenched and tempered steels has a much weaker dependency on bulk hardness [9]. The use of hardness as a parameter for predicting the wear behaviour of materials must be done with caution since, very often they are not in correlation [10].

The relationship between obtained wear values with hardness of tested materials is shown in [Figure 6](#). For better comparison wear is expressed through the relative values of hardness and wear resistance (reciprocating value of the wear rate). Coating Ni was taken as a reference material and relative hardness and wear resistance for this coating are equal to 1. Coating Ni^{HT}, for instance, is harder by approximately 10 % (relative hardness of 1.09), and possesses more than twice higher resistance to wear (relative wear resistance of 2.15) than reference coating Ni.

The first feature from [Figure 6](#) is that the hardest coating shows highest wear resistance as well (coating Ni-BN^{HT}), but from the other coatings it is obvious that relationship between the abrasive wear and hardness values of any kind did not exist.

4. CONCLUSIONS

Four different chemical Ni coatings were investigated on abrasive wear resistance. Influence of heat treatment (heating at 300 °C for 6 hours) and addition of BN nanoparticles (5 vol. % of 10 nm average size) on dry abrasive wear was analysed.

Heat treatment provided less stable wear process, but significantly decreases the abrasive wear rate (by approximately 54%).

Addition (imbedding) of BN nanoparticles also decreased the abrasive wear rate, but the decrease was lesser (by approximately 40%). The smallest wear rate was noticed for heat treated Ni coating with imbedded BN nanoparticles (wear rate decrease was approximately 72%).

Correlation of any kind between hardness and wear resistance of tested coatings could not be established.

5. ACKNOWLEDGEMENTS

The research presented in the paper is partly supported by the following projects: (a) the project AComIn “Advanced Computing for Innovation”, grant 316087, funded by the FP7 Capacity Programme (Research Potential of Convergence Regions); (b) by the tasks under the Project ДУНК-01/3 “University R&D Complex for innovation and transfer of knowledge in micro/nano-technologies and materials, energy efficiency and virtual engineering” funded by the Bulgarian Ministry of Education and Science, and (c) by the tasks of the International cooperation agreement between the Faculty of Industrial Technology at TU-Sofia and the Faculty of Mechanical Engineering at the University of Belgrade.

6. REFERENCES

1. Oswald, T.A., Hernández-Ortiz, J.P., Polymer Processing: Modelling and Simulation, Carl Hanser Verlag, Munich. (2006)
2. Frydel J., Mewes D., Luther S., Schuster R.H., Rubber sheets calendaring: Contribution to preventing the occurrence of gas entrapments, Kautschuk, Gummi, Kunststoffe, 61 (2008) 286-293.
3. Kandeve M., Karastoyanov D., Andonova A., Wear and tribothermal effects of nano-structured nickel chemical coatings, Applied Mechanics and Materials, 157-158 (2012) 960-963.

4. Assenova E., Kandeveva M., Self-organization in tribology: The role of synergism and selective transfer, Proceedings of the 7th International Conference on Tribology – BALKANTRIB '11 03-05 October 2011 Thessaloniki, Greece, 2011, pp: 305-310.
5. Kandeveva M., Karastoyanov D., Ivanova B., Dimitrova A., Sofronov Y., Nikolov N., Friction and wear of Ni coatings with nanosize particles of SiC, Proceedings of the 5th World Tribology Congress (WTC 2013) 08-13 September 2013 Turin, Italy, 2013, paper: 1241.
6. Gavrilov, G., Nicolov, C., Electroless Nickel and Composite Coatings, Technika, Sofia. (1985)
7. Karaguiozova Z., Stavrev S., Babul T., Ciski A., Influence of cubic nanostructure additions on the properties of electroless coatings, International Journal of Nanomanufacturing, 5 (2010) 129-138.
8. Khruschov, M.M., Resistance of metals to wear by abrasion, as related to hardness, Proceedings of the International Conference on Lubrication and Wear 01-03 October 1957 London, UK, 1957, pp: 654-658.
9. Sundararajan, G., The differential effect of the hardness of metallic materials on their erosion and abrasion resistance, Wear, 162-164 (1993) 773-781.
10. Vencl A., Manić N., Popovic V., Mrdak M., Possibility of the abrasive wear resistance determination with scratch tester, Tribology Letters, 37 (2010) 591-604.